


AD-A043 659

FRANK J SEILER RESEARCH LAB UNITED STATES AIR FORCE --ETC F/6 10/3
HIGH ENERGY DENSITY PELLETIZED ALUMINUM CHLORIDE THERMAL BATTER--ETC(U)
APR 77 J C NARDI, J K ERBACHER, C L HUSSEY
FJSRL-TR-77-0004

UNCLASSIFIED

NL

1 OF 1
AD
A043659

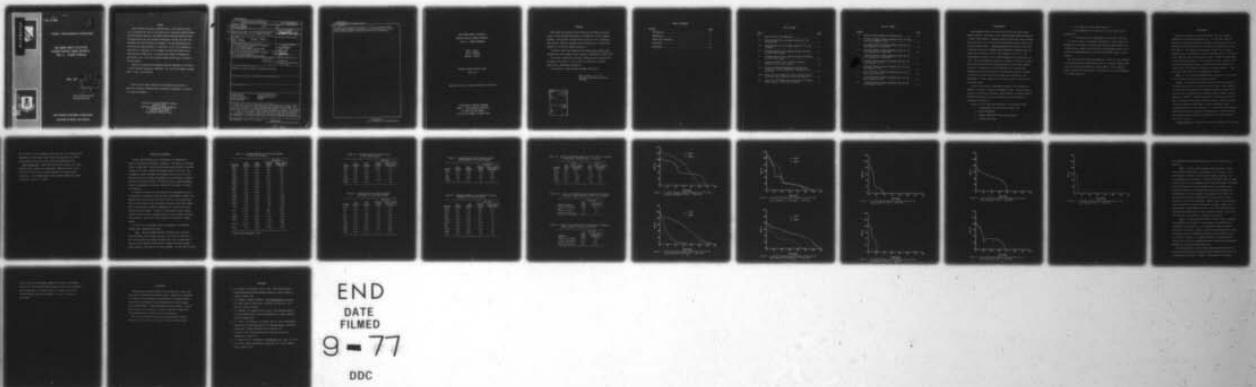

END
DATE
FILMED
9-77
DDC

ADA 043659



77-
FJSRL-TR-0004


12

B.S.

FRANK J. SEILER RESEARCH LABORATORY

**HIGH ENERGY DENSITY PELLETIZED
ALUMINUM CHLORIDE THERMAL BATTERIES:
PART II. CATHODE SCREENING**

APRIL 1977

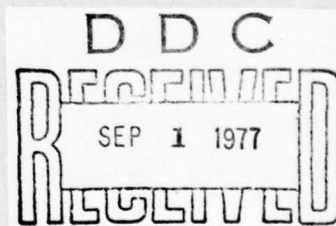

APPROVED FOR PUBLIC RELEASE;
DISTRIBUTION UNLIMITED.



**AIR FORCE SYSTEMS COMMAND
UNITED STATES AIR FORCE**

NOTICE

When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data, is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

Inquiries concerning this document should be addressed to the Frank J. Seiler Research Laboratory (FJSRL/NC), U.S. Air Force Academy, Colorado 80840. Phone - 303-472-2655.

Copies of this report should not be returned unless return is required by security considerations, contractual obligations, or notice on a specific document.

Printed in the United States of America
Available from
National Technical Information Service
U.S. Department of Commerce
5285 Port Royal Road
Springfield, Virginia 22151

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

| REPORT DOCUMENTATION PAGE | | READ INSTRUCTIONS BEFORE COMPLETING FORM |
|---|------------------------------|--|
| 1. REPORT NUMBER FJSRL-TR-77-0004 | 2. GOVT ACCESSION NO. ADA | 3. RECIPIENT'S CATALOG NUMBER |
| 4. TITLE (and Subtitle) High Energy Density Pelletized Aluminum Chloride Thermal Batteries: Part II. Cathode Screening. | | 5. TYPE OF REPORT & PERIOD COVERED Technical Report, Jan 1976-Apr 1977 |
| 7. AUTHOR(s) John C. Nardi, Charles L. Hussey John K. Erbacher | | 6. PERFORMING ORG. REPORT NUMBER |
| 9. PERFORMING ORGANIZATION NAME AND ADDRESS F. J. Seiler Research Laboratory (FJSRL/NC) Air Force Systems Command U. S. Air Force Academy, Colorado 80840 | | 10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS 61102F/2303/F2/07 |
| 11. CONTROLLING OFFICE NAME AND ADDRESS F. J. Seiler Research Laboratory (FJSRL/NC) Air Force Systems Command U. S. Air Force Academy, Colorado 80840 | | 12. REPORT DATE Apr 1977 |
| 14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) <i>12 31p.</i> | | 13. NUMBER OF PAGES 22 |
| 16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited. | | 15. SECURITY CLASS. (of this report) Unclassified |
| 17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report) | | 15a. DECLASSIFICATION/DOWNGRADING SCHEDULE N/A |
| 18. SUPPLEMENTARY NOTES <i>A021 748</i> | | |
| 19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Thermal Battery Tellurium Tetrachloride Aluminum Chloride Tetrachloroaluminate Tungsten Hexachloride Graphite Iron Trichloride | | |
| 20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Pelletized single cell experiments have been conducted to develop a family of potential cathodes for a new, low temperature thermal battery system. The cells utilize a 60.2 a/o lithium-aluminum alloy anode and a molten salt electrolyte of NaCl-saturated $AlCl_3$. They operate at temperatures between 175 and 250°C. A total of 40 sulfides, oxides, and halides were evaluated and compared to the molybdenum(V) chloride and copper(II) chloride cathodes previously studied. Of this group, three halides, WCl_6 , $FeCl_3$, and $TeCl_4$, exhibited long discharge | | |

DD FORM 1 JAN 73 1473 EDITION OF 1 NOV 65 IS OBSOLETE

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

319 920

mt

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

20. Continued.

lifetimes, high available energy density, and high voltages under load. Various brands of graphite, acetylene black, and various types of metallic current collectors also were evaluated for performance enhancement.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

HIGH ENERGY DENSITY PELLETIZED
ALUMINUM CHLORIDE THERMAL BATTERIES:
PART II. CATHODE SCREENING

JOHN C. NARDI
JOHN K. ERBACHER
CHARLES L. HUSSEY

TECHNICAL REPORT SRL-TR-77-0004

APRIL 1977

Approved for public release; distribution unlimited

DIRECTORATE OF CHEMICAL SCIENCES
FRANK J. SEILER RESEARCH LABORATORY
AIR FORCE SYSTEMS COMMAND
US AIR FORCE ACADEMY, COLORADO 80840

FOREWORD

This report was prepared by the Directorate of Chemical Sciences, Frank J. Seiler Research Laboratory, United States Air Force Academy, Colorado. The work was initiated under Project No. 2303, "Chemistry," Task 2303-F2, "Physical Chemistry and Electrochemistry," Work Unit No. 2303-F2-07, "Pelletized Thermal Batteries."

The report covers work conducted from January 1976 to April 1977. The manuscript was released by the authors for publication in April 1977.

The authors acknowledge the helpful discussions they received from A. Baldwin, D.M. Bush, S.C. Levy, and B.H. Van Domelen of Sandia Laboratories, Albuquerque, New Mexico.

This technical report has been reviewed and approved.

BEN A. LOVING, LtCol, USAF
Director, Directorate of Chemical
Sciences

| | |
|---------------------------------|---|
| ACCESSION for | |
| NTIS | White Section <input checked="" type="checkbox"/> |
| DDC | Buff Section <input type="checkbox"/> |
| UNANNOUNCED | <input type="checkbox"/> |
| JUSTIFICATION | |
| BY | |
| DISTRIBUTION/AVAILABILITY CODES | |
| Dis: and/or SPECIAL | |
| A | |

TABLE OF CONTENTS

| <u>Section</u> | <u>Page</u> |
|----------------------------------|-------------|
| Introduction | 1 |
| Experimental | 3 |
| Results and Discussion | 7 |
| Future Work | 21 |
| References | 22 |

LIST OF TABLES

| <u>Table</u> | | <u>Page</u> |
|--------------|---|-------------|
| I | Typical Single Cell Composition | 4 |
| II | Discharge Results for the Metal Chlorides at 175°C and 15 mA/cm ² | 8 |
| III | Discharge Results for the Metal Oxides at 175°C and 15 mA/cm ² | 9 |
| IV | Discharge Results for the Metal Sulfides and Sulfur at 175°C and 15 mA/cm ² | 9 |
| V | Discharge Results for the Metal Florides and Bromides at 175°C and 15 mA/cm ² | 10 |
| VI | Discharge Results for the "Top Ten" Potential Cathodes at 175°C and 15 mA/cm ² | 10 |
| VII | Cathode Performance Comparison to 80% ICCV as a Function of Operating Temperature (Discharge Rate = 15 mA/cm ²) | 11 |
| VIII | Single Cell Performance for Various Internal Current Collectors (MoCl ₅ Cathode at 175°C and 15 mA/cm ²) | 11 |
| IX | Single Cell Performance for Various Types of Graphite (MoCl ₅ Cathode at 175°C and 15 mA/cm ²) | 11 |

LIST OF FIGURES

| <u>Figure</u> | | <u>Page</u> |
|---------------|--|-------------|
| 1 | Typical Trilayer Single Cell Configuration | 5 |
| 2 | 15 mA/cm ² Constant Current Discharge Curves for MoCl ₅ and CuCl ₂ Cathodes at 175°C | 12 |
| 3 | 15 mA/cm ² Constant Current Discharge Curves for the WCl ₆ Cathode at 175 and 250°C | 12 |
| 4 | 15 mA/cm ² Constant Current Discharge Curves for the FeCl ₃ Cathode at 175 and 250°C | 13 |
| 5 | 15 mA/cm ² Constant Current Discharge Curves for the TeCl ₄ Cathode at 175 and 250°C | 13 |
| 6 | 15 mA/cm ² Constant Current Discharge Curve for the Fe ₂ O ₃ Cathode at 175°C | 14 |
| 7 | 15 mA/cm ² Constant Current Discharge Curve for the CuO Cathode at 175°C | 14 |
| 8 | 15 mA/cm ² Constant Current Discharge Curve for the NbCl ₅ Cathode at 175°C | 15 |
| 9 | 15 mA/cm ² Constant Current Discharge Curve for the HgCl ₂ Cathode at 175°C | 15 |
| 10 | 15 mA/cm ² Constant Current Discharge Curve for the Cu ₂ S Cathode at 175°C | 16 |

INTRODUCTION

Many compounds exist which theoretically would make good thermal battery cathodes. The object of this second cathode screening study was to select those materials compatible with the electrolyte (NaCl-saturated AlCl_3) and anode (60.2 a/o LiAl alloy) which would warrant further, more detailed investigations. Compounds investigated during this study were identified as potential cathodes during experiments conducted after the completion of the first study in this laboratory in 1976 (1). The electrochemical system utilizes a NaCl-saturated AlCl_3 electrolyte, m.p. 158°C . This electrochemical system is a candidate to replace or complement current thermal battery systems operating at much higher temperatures (2). Previous work in this laboratory (3,4) revealed that molybdenum(V) chloride and copper(II) chloride were potential cathodes for pelletized thermal batteries utilizing this electrolyte. The performance of these cathodes will be used to provide a "baseline" for the present study.

A total of 40 inorganic compounds was tested: this included 24 halides, 9 sulfides, 6 oxides, and elemental sulfur. Various brands of purified and unpurified graphites, acetylene black, and several metallic compounds were used as current collectors and were evaluated as to performance enhancement.

The main criteria that were considered in our evaluation were:

1. A reproducible high open circuit voltage, OCV.
2. Thermal efficiency.
3. Chemical compatibility with the electrolyte.
4. Coulombic efficiency.

5. Low solubility of the cathode material.
6. Long discharge life to 80% of the initial closed circuit voltage, ICCV.
7. Low polarization as evidenced by a low iR drop under load.

In a typical operational battery configuration, voltage constraints imposed by the electronic circuitry often require voltage cutoffs of 80% of peak voltage. Based on this criterion, the compounds tested in this study were ordered according to their delivered energy density to this voltage.

The results of this study are preliminary in that the cell configuration tested had been optimized specifically for the MoCl_5 cathode, which is not necessarily the optimum for other cathodes. Those compounds showing promise will be optimized in a manner similar to that undertaken in the MoCl_5 study (4).

EXPERIMENTAL

Electrolyte preparation, pellet fabrication, and cell discharge experiments were described previously (1). The individual anode and separating electrolyte weights were identical to those used in the $\text{LiAl}/\text{NaAlCl}_4/\text{MoCl}_5$ optimized single cell (4) and were unchanged for all tests (see Table I). The graphite and electrolyte content in the cathode compartment were also identical to those in the MoCl_5 cell. To facilitate direct comparison with cells containing a MoCl_5 cathode, the same amount of each new cathode material, 3.44 millimoles, was used. Several of the compounds evaluated were known to be semiconductor materials and were tested both with and without the addition of powdered graphite. A complete pelletized single cell is illustrated in Figure 1.

Anode: 60.2 a/o lithium-aluminum powder was obtained from the Foote Mineral Company and used without further treatment.

Cathode: The Results and Discussion section contains information on the source and purity of the cathode materials tested. Those compounds not specifically discussed were a minimum 99.0% pure and obtained from the Alfa-Ventron Corporation or the Research Organic/Inorganic Chemical Corporation (ROC/RIC). Graphite (grade #38) and acetylene black were used as obtained from the Fisher Scientific Company. Superior graphite flakes were purified at 600°C under a chlorine atmosphere using a procedure developed in this laboratory (1). Some of the Fisher graphite samples were purified by boiling for one-half hour in concentrated HCl . This graphite was then washed with distilled water, suction filtered and dried in an oven.

Current Collectors: Five mil nickel foil (Alfa-Ventron), 99.98% pure,

Table I. Typical Single Cell Composition

| Section | Weight (g) | Component |
|-----------|------------|-------------------------|
| Anode | 0.27 | 60.2 a/o LiAl |
| Separator | 0.78 | EB Mixture ^a |
| Cathode | 0.64 | EB Mixture ^a |
| | b | Cathode Material |
| | 0.23 | Graphite |

^aEB Mixture: Electrolyte (49.85 m/o AlCl_3 -
50.15 m/o NaCl) + Binder
(10 w/o Cab-O-Sil)

^b3.44 millimoles of cathode material

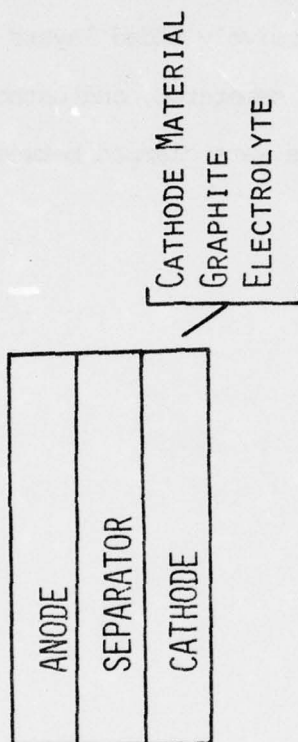


Figure 1. Typical Trilayer Single Cell Configuration

was cut into 1.125 inch diameter circles with tab. The collectors were burnished with emery paper, washed with distilled water and acetone, stored under dry argon, and again lightly burnished before use.

Pellet Fabrication: Three-layer pellets were formed in all cases. Pressures used to compact the successively added layers were 16,700, 23,000 and 29,200 lb/in² for anode, separator, and cathode layers respectively. The assembled pellets were clamped between the platens of the cell tester at 4.5 lb/in².

RESULTS AND DISCUSSION

The data obtained during this investigation are summarized in Tables II through IX and Figures 2 through 10. The tables give the open circuit voltage (OCV), initial closed circuit voltage (ICCV), the active lifetime to 80% ICCV, and delivered energy density at 80% ICCV. The accompanying figures represent the discharge curves to zero volts for each of the top ten cathodes as determined in this evaluation, based on the 80% ICCV lifetime criteria. The MoCl_5 and CuCl_2 cathode discharge curves as investigated in previous studies (3,4) are shown in Figure 2 for comparison.

An important consideration when analyzing the experimental data is the application intended for the particular electrochemical system. For example, MoCl_5 with its high OCV could be used as a high energy output thermal battery whereas CuCl_2 would make an excellent low energy output, long lifetime thermal battery as evidenced by its lower OCV but long, flatter discharge plateau. To obtain the advantages of both cathodes, a thermal battery could be developed using a mixture of MoCl_5 and CuCl_2 as the cathode. Mixed cells of this type will be examined in future studies.

In view of their noticeably superior performance, the following cathodes were investigated in detail.

WCl_6 : The WCl_6 cathode (ROC/RIC, 99% pure) gave a cell OCV which was between that of MoCl_5 and CuCl_2 . The initial iR drop for a cell containing WCl_6 was similar to these cells, but a steeper drop in the cell voltage discharge curve led to a shorter life and available energy density to 80% ICCV at 175°C and 15 mA/cm^2 . At 250°C and 15 mA/cm^2 ,

Table II. Discharge Results for the Metal Chlorides
at 175°C and 15 mA/cm²

| Chloride | OCV (Volts) | ICCV (Volts) | 80% ICCV | |
|---------------------|----------------|-----------------|-------------------|-----------------------------|
| | | | Lifetime (Min) | Energy Density (W-hr/lb) |
| MoCl ₅ | 2.40 | 2.31 | 30.0 | 16.3 |
| CuCl ₂ | 1.83 | 1.72 | 36.5 | 13.8 |
| WCl ₆ | 2.16 | 2.05 | 23.7 | 9.1 |
| FeCl ₃ | 2.29 | 2.17 | 13.3 | 7.9 |
| TeCl ₄ | 1.73 | 1.66 | 15.7 | 6.0 |
| NbCl ₅ | 1.70 | 1.59 | 11.0 | 3.8 |
| HgCl ₂ | 1.78 | 1.68 | 9.7 | 3.8 |
| CoCl ₂ | 1.14 | 0.86 | 10.9 | 2.5 |
| MoCl ₃ | 2.11 | 1.97 | 3.6 | 1.6 |
| VCl ₃ | 1.99 | 1.80 | 3.4 | 1.6 |
| BiCl ₃ | 1.33 | 1.13 | 5.0 | 1.23 |
| CrCl ₃ | 1.64 | 1.33 | 2.2 | 0.76 |
| TaCl ₅ | 1.58 | 1.29 | 2.9 | 0.73 |
| RuCl ₃ | 1.72 | 1.57 | 1.6 | 0.64 |
| NiCl ₂ | 1.35 | 1.01 | 2.0 | 0.52 |
| CuCl* | 1.85 | 1.76 | 0.7 | 0.37 |
| | 1.07 | 0.86 | 45.6 | 12.2 |
| CrCl ₂ | 1.20 | 1.11 | 0.6 | 0.18 |
| ZrCl ₄ | 1.14 | 0.87 | 0.4 | 0.10 |
| MnCl ₂ | 1.39 | 1.08 | 0.02 | 0.05 |
| FeCl ₂ * | 1.64 | 1.50 | 0.01 | 0.04 |
| | 0.63 | 0.50 | 25.0 | 3.56 |
| TiCl ₃ | 1.18 | 0.94 | 0.01 | 0.02 |

* Double entry discussed in text

Table III. Discharge Results for Metal Oxides
at 175°C and 15 mA/cm²

| Oxide | OCV (Volts) | ICCV (Volts) | 80% ICCV | |
|--------------------------------|----------------|-----------------|-------------------|-----------------------------|
| | | | Lifetime (Min) | Energy Density (W-hr/lb) |
| Fe ₂ O ₃ | 1.86 | 1.72 | 10.8 | 5.0 |
| CuO | 1.85 | 1.76 | 8.3 | 4.5 |
| Cu ₂ O | 1.09 | 1.00 | 5.5 | 1.6 |
| V ₂ O ₅ | 2.20 | 2.01 | 1.9 | 1.0 |
| Fe ₃ O ₄ | 1.59 | 1.44 | 1.8 | 0.6 |
| Sb ₂ O ₃ | 0.45 | 0.12 | 0.3 | 0.0 |

Table IV. Discharge Results for Metal Sulfides
and Sulfur at 175°C and 15 mA/cm²

| Sulfide | OCV (Volts) | ICCV (Volts) | 80% ICCV | |
|-------------------|----------------|-----------------|-------------------|-----------------------------|
| | | | Lifetime (Min) | Energy Density (W-hr/lb) |
| Cu ₂ S | 1.43 | 1.35 | 7.0 | 2.50 |
| CuS | 1.68 | 1.58 | 3.9 | 1.81 |
| S ₈ | 1.48 | 1.10 | 3.2 | 0.77 |
| TiS ₂ | 1.43 | 1.33 | 2.0 | 0.70 |
| MnS | 1.21 | 0.96 | 2.2 | 0.60 |
| TaS ₂ | 1.23 | 1.05 | 0.8 | 0.21 |
| Tl ₂ S | 1.41 | 1.21 | 1.0 | 0.21 |
| ZrS ₂ | 0.74 | 0.62 | 1.0 | 0.14 |
| FeS ₂ | 0.98 | 0.71 | 0.2 | 0.03 |
| FeS | 0.94 | 0.77 | 0.1 | 0.03 |

Table V. Discharge Results for the Metal Fluorides and Bromides at 175°C and 15 mA/cm²

| Halide | OCV (Volts) | ICCV (Volts) | 80% ICCV | |
|-------------------|----------------|-----------------|-------------------|-----------------------------|
| | | | Lifetime (Min) | Energy Density (W-hr/lb) |
| SbF ₅ | 2.18 | 2.00 | 2.2 | 1.09 |
| VF ₄ | 1.88 | 1.66 | 1.4 | 0.63 |
| VBr ₃ | 1.60 | 1.44 | 0.1 | 0.26 |
| MoBr ₂ | 1.38 | 1.01 | 0.1 | 0.12 |

Table VI. Discharge Results for the "Top Ten" Potential Cathodes at 175°C and 15 mA/cm²

| Cathode | OCV (Volts) | ICCV (Volts) | 80% ICCV | |
|--------------------------------|----------------|-----------------|-------------------|-----------------------------|
| | | | Lifetime (Min) | Energy Density (W-hr/lb) |
| MoCl ₅ | 2.40 | 2.31 | 30.0 | 16.3 |
| CuCl ₂ | 1.83 | 1.72 | 36.5 | 13.8 |
| WCl ₆ | 2.16 | 2.05 | 23.7 | 9.1 |
| FeCl ₃ | 2.20 | 2.17 | 13.3 | 7.9 |
| TeCl ₄ | 1.73 | 1.66 | 15.7 | 6.0 |
| Fe ₂ O ₃ | 1.86 | 1.72 | 10.8 | 5.0 |
| CuO | 1.85 | 1.76 | 8.3 | 4.5 |
| NbCl ₅ | 1.70 | 1.59 | 11.0 | 3.8 |
| HgCl ₂ | 1.78 | 1.68 | 9.7 | 3.8 |
| Cu ₂ S | 1.43 | 1.35 | 7.0 | 2.5 |

Table VII. Cathode Performance Comparison to 80% ICCV as a Function of Temperature (Discharge Rate = 15 mA/cm²)

| Cathode | 175°C | | 250°C | |
|-------------------|------------|--------------------------|------------|--------------------------|
| | Time (Min) | Energy Density (W-hr/lb) | Time (Min) | Energy Density (W-hr/lb) |
| MoCl ₅ | 30.0 | 16.3 | 12.3 | 6.80 |
| CuCl ₂ | 36.5 | 13.8 | 5.33 | 3.25 |
| WCl ₆ | 23.7 | 9.10 | 6.33 | 2.41 |
| FeCl ₃ | 13.3 | 7.90 | 12.3 | 7.61 |
| TeCl ₄ | 15.7 | 6.00 | 7.33 | 2.65 |

Table VIII. Single Cell Performance for Various Internal Current Collectors (MoCl₅ Cathode at 175°C and 15 mA/cm²)

| Current Collector | 80% ICCV | |
|-----------------------|------------|--------------------------|
| | Time (Min) | Energy Density (W-hr/lb) |
| Graphite (grade #38) | 30.0 | 16.3 |
| Nickel (5 micron) | 1.0 | 0.6 |
| Molybdenum (200 mesh) | 0.2 | 0.2 |

Table IX. Single Cell Performance for Various Types of Graphite (MoCl₅ Cathode at 175°C and 15 mA/cm²)

| Graphite | 80% ICCV | |
|---------------------|------------|--------------------------|
| | Time (Min) | Energy Density (W-hr/lb) |
| Fisher (HCl boiled) | 31.7 | 17.1 |
| Fisher (unpurified) | 30.0 | 16.3 |
| Superior (purified) | 24.3 | 13.2 |

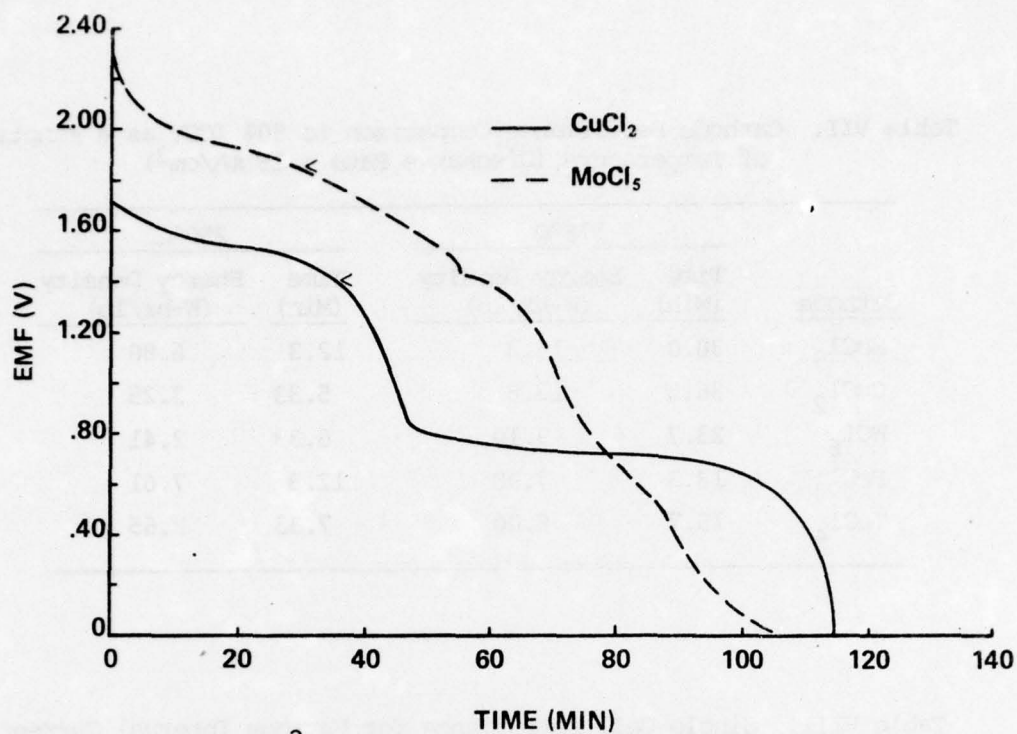


Figure 2. 15 mA/cm^2 Constant Current Discharge Curves for MoCl_5 and CuCl_2 Cathodes at 175°C . \times , 80% ICCV.

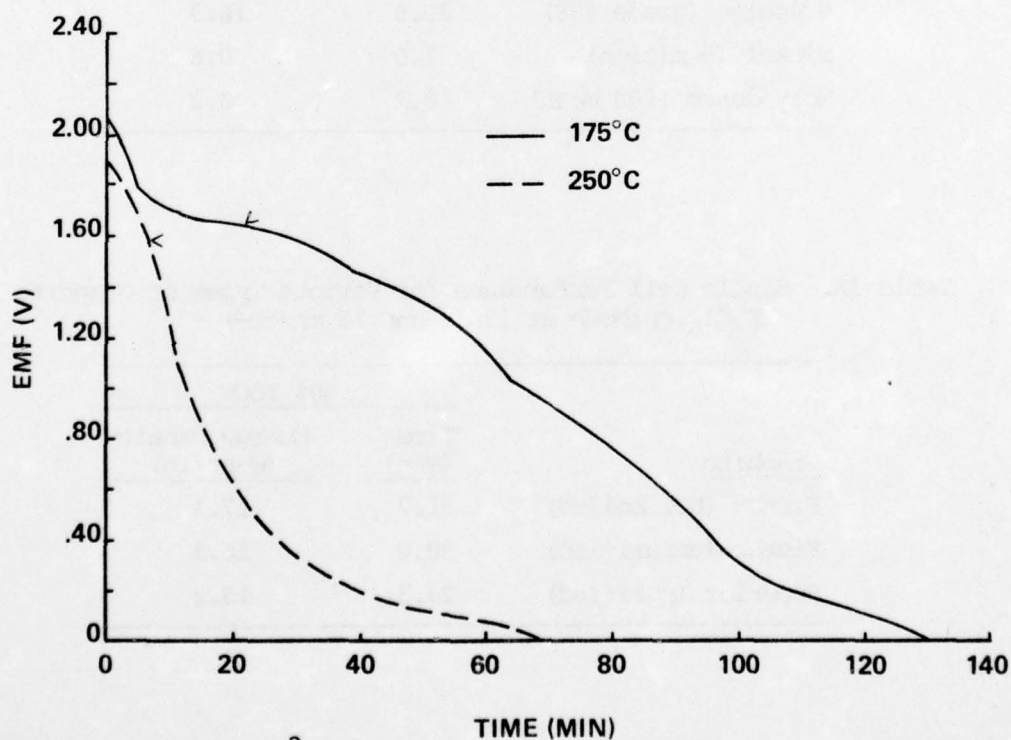


Figure 3. 15 mA/cm^2 Constant Current Discharge Curves for the WCl_6 Cathode at 175 and 250°C . \times , 80% ICCV.

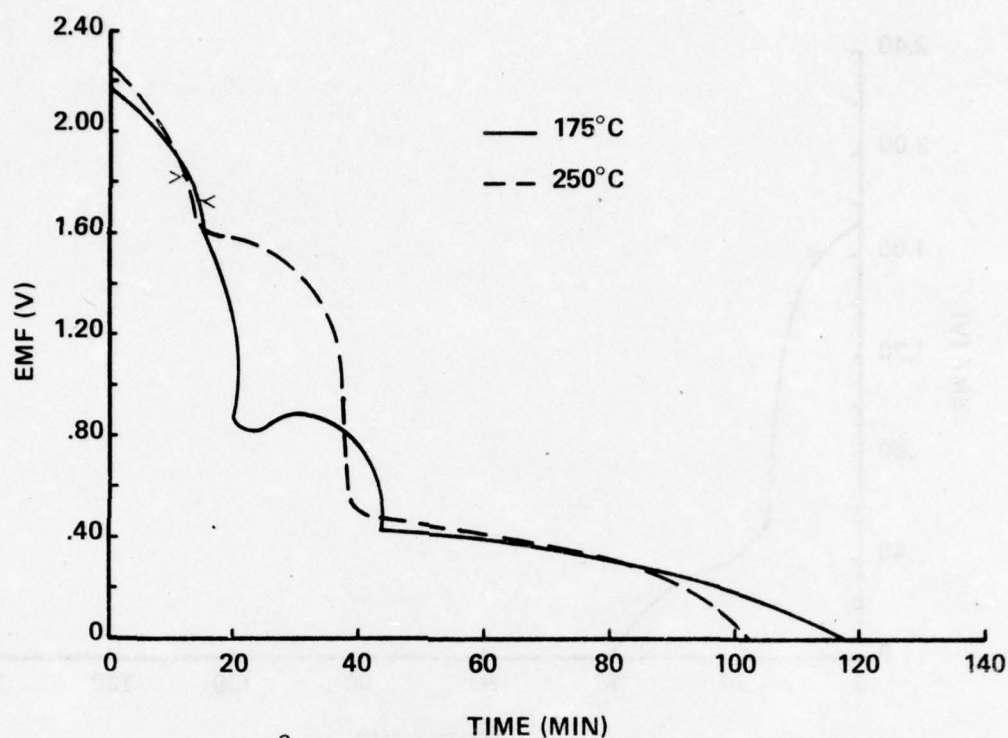


Figure 4. 15 mA/cm^2 Constant Current Discharge Curves for the FeCl_3 Cathode at 175 and 250°C. \angle , 80% ICCV.

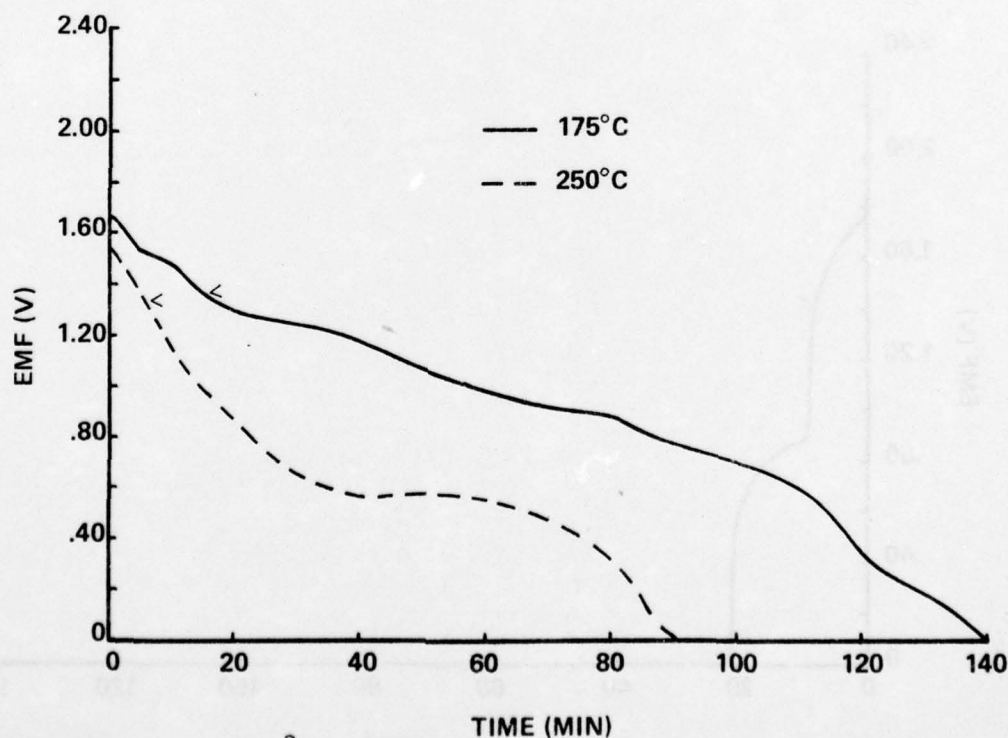


Figure 5. 15 mA/cm^2 Constant Current Discharge Curves for the TeCl_4 Cathode at 175 and 250°C. \angle , 80% ICCV.

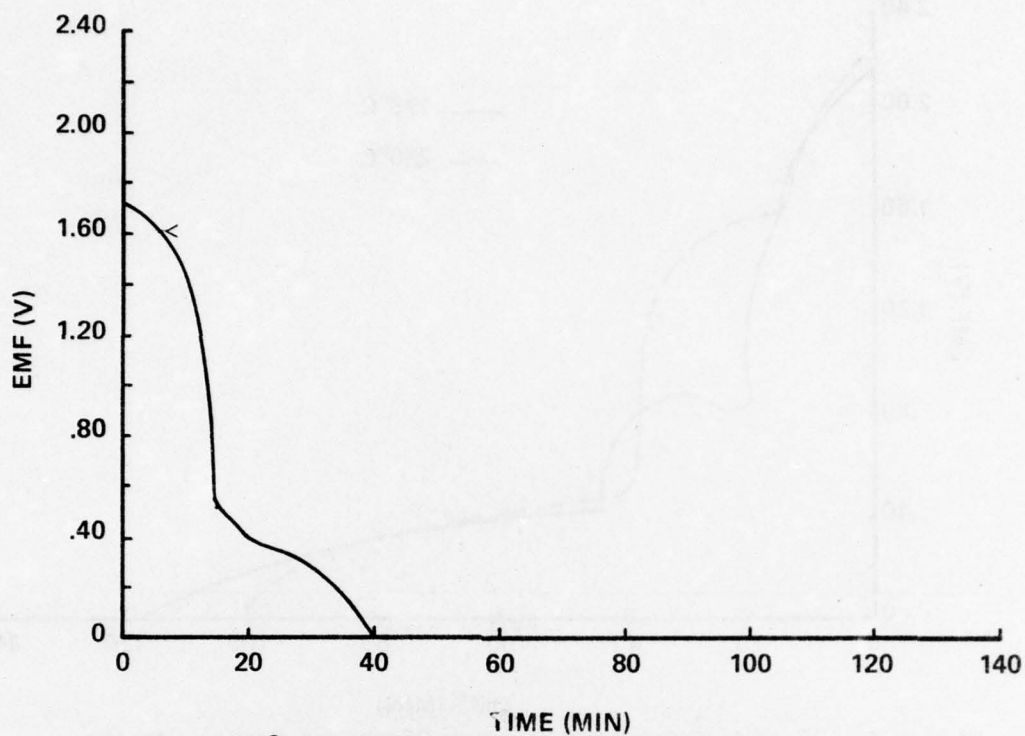


Figure 6. 15 mA/cm^2 Constant Current Discharge Curve for the Fe_2O_3 Cathode at 175°C . <, 80% ICCV.

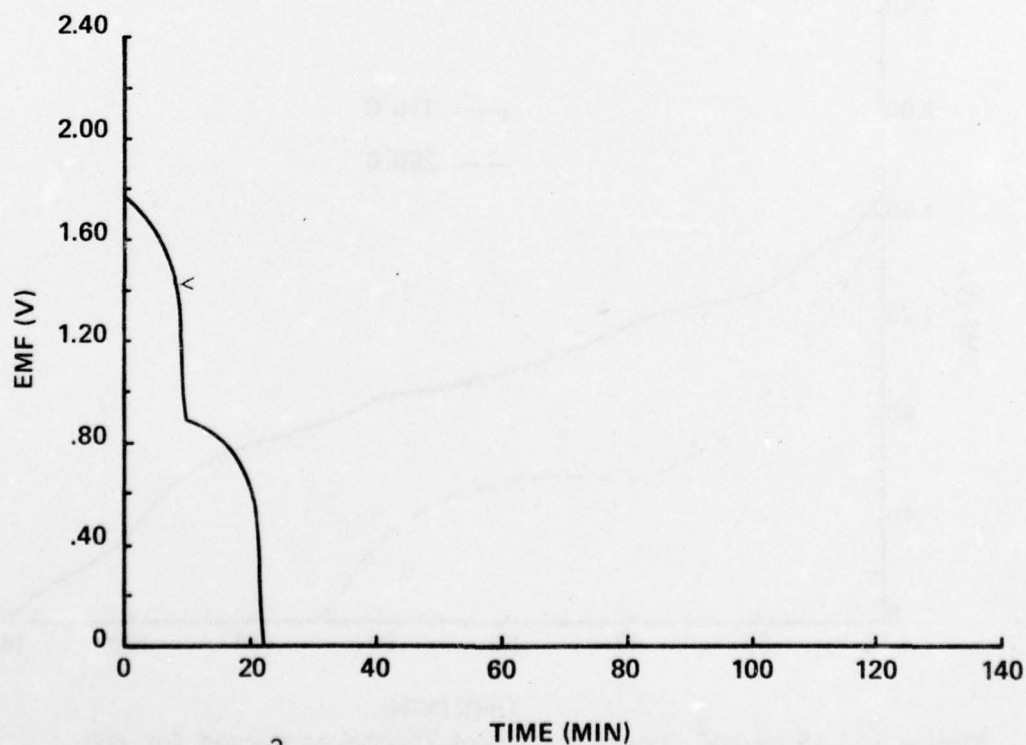


Figure 7. 15 mA/cm^2 Constant Current Discharge Curve for the CuO Cathode at 175°C . <, 30% ICCV.

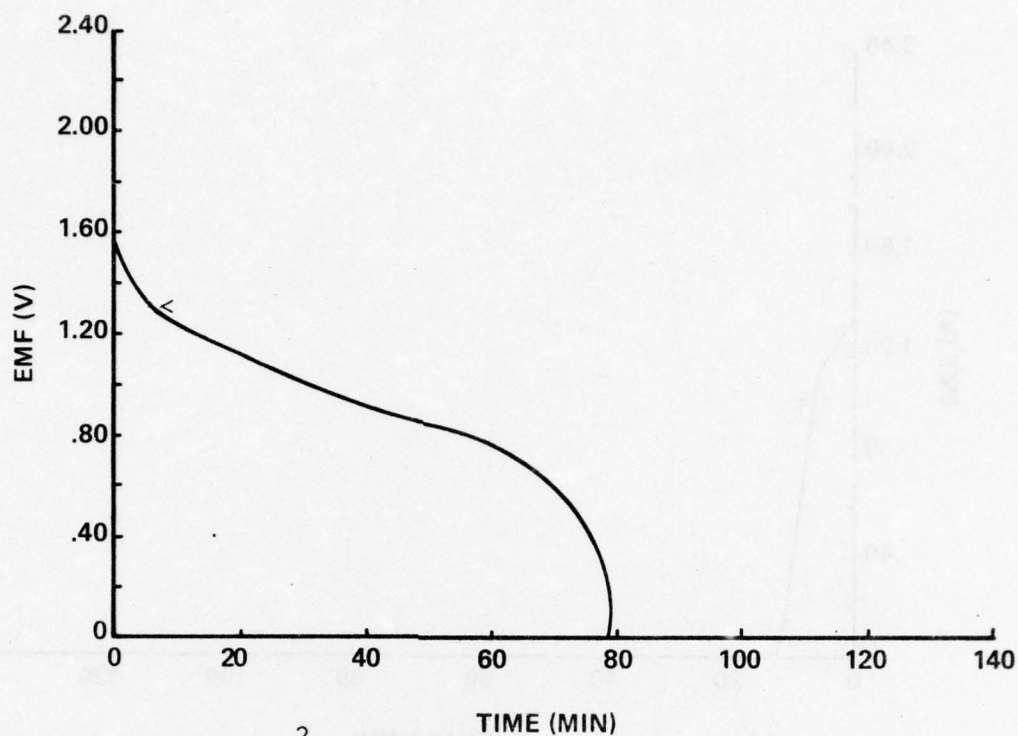


Figure 8. 15 mA/cm^2 Constant Current Discharge Curve for the NbCl_5 Cathode at 175°C . \leftarrow , 80% ICCV.

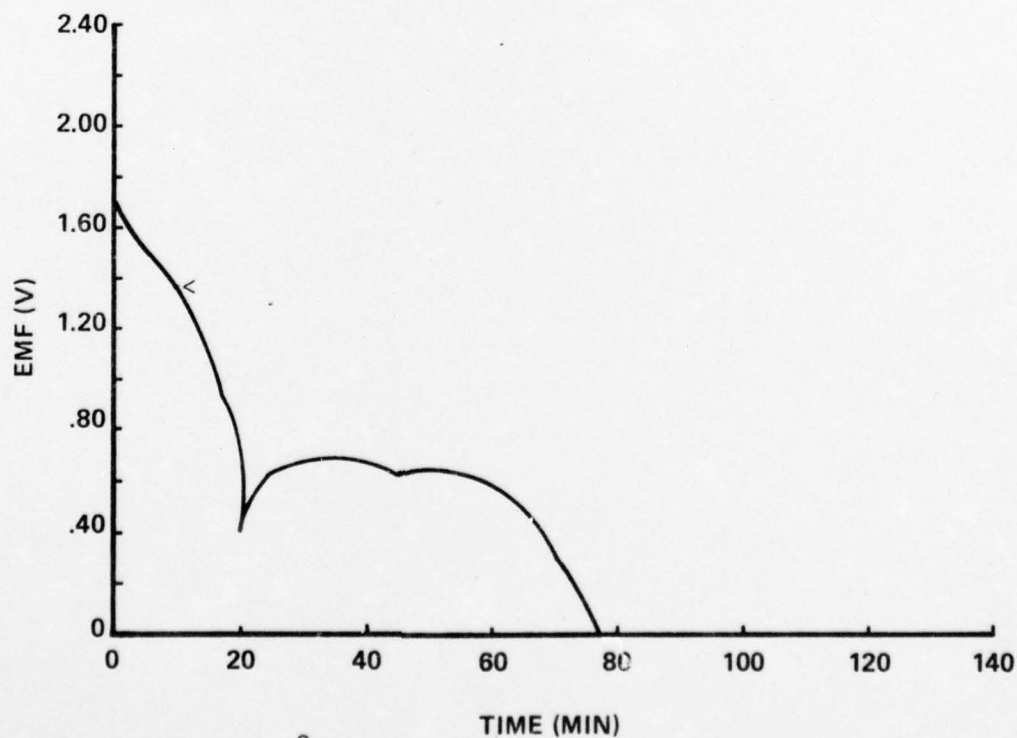


Figure 9. 15 mA/cm^2 Constant Current Discharge Curve for the HgCl_2 Cathode at 175°C . \leftarrow , 80% ICCV.

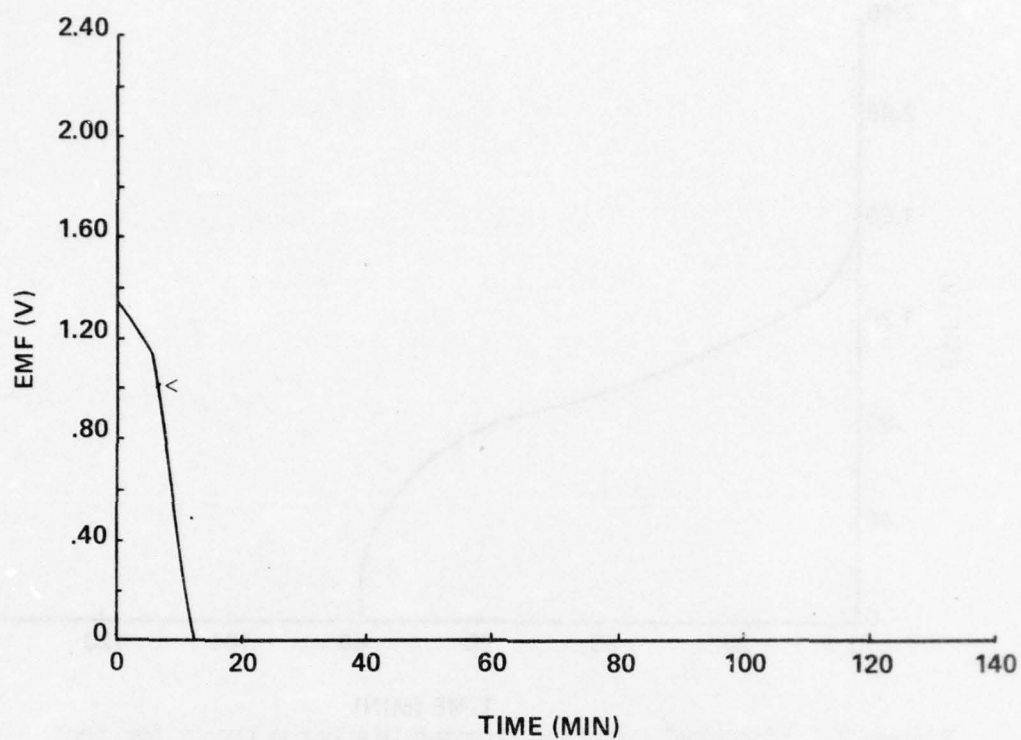


Figure 10. 15 mA/cm^2 Constant Current Discharge Curve for the Cu_2S Cathode at 175°C . <, 80% ICCV.

the performance deteriorated drastically, as shown in Figure 3 and Table VII.

FeCl₃: The FeCl₃ (MC/B, 99% pure) had a very small iR drop from a relatively high open circuit potential of 2.20 volts. It has the additional advantage of being cheap and readily available. The FeCl₃ discharge curve (Figure 4) at 175°C and 15 mA/cm² showed a voltage increase after the first discharge plateau had been attained. We suggest that this increase is due to the dissolution of an insoluble FeCl₂ surface film formed on the cathode during the initial discharge (6). At temperatures of 250°C and above, the discharge curve (Figure 4) is flatter with no voltage irregularities and there is only a slight decrease in the 80% ICCV performance. Because there is little degradation in performance at higher temperatures, the FeCl₃ cathode can be operated over a wider temperature range. This would simplify the manufacturing and quality control of FeCl₃ thermal batteries, especially in the selection of heat paper of a suitable caloric value.

TeCl₄: The TeCl₄ cathode (ROC/RIC, 99% pure) gave an extremely flat discharge curve (Figure 5), the flattest yet observed with the exception of CuCl₂ (Figure 2). It also had the longest lifetime to zero volts, 140 minutes. However, the 80% ICCV performance data suggest an inferior output as compared to the WCl₆ or FeCl₃ cathodes at both 175 and 250°C (Figure 5). In addition, TeCl₄ is a highly poisonous chemical and its use as a cathode may present manufacturing and handling problems for production thermal batteries.

The discharge behavior of the other cathodes evaluated fell well below the performance of the above mentioned cathodes and thus will not be discussed in any detail. However, an explanation of the double

entries in Table II for the FeCl_2 and CuCl cathodes is necessary.

The discharge curve of CuCl (Baker, 96.4% pure) shows a significant voltage drop upon application of a 15 mA/cm^2 load. As a result the 80% ICCV lifetime and energy density were very low. If, however, the 80% ICCV performance is measured from an OCV value determined in an electrochemical study of copper in the tetrachloroaluminate melt (6), the 80% ICCV output is more respectable. The 80% lifetime was 45.6 minutes and energy density was 12.2 W-hr/lb. The OCV of copper(I) chloride which was observed in this study was similar to that of copper(II) chloride, indicating the probable presence of copper(II) as an impurity in the commercially obtained copper(I) chloride. If all of the copper(II) could be removed, a cathode consisting of only copper(I) chloride would make an excellent long life, low output thermal battery.

A similar argument can be made for the iron(II) chloride cathode. The large voltage drop gave a poor 80% ICCV performance. However, the correct $\text{Fe}^{2+}/\text{Fe}^0$ potential was reported to be 0.63V (6). Use of the latter value leads to an 80% ICCV lifetime and energy density of 25.0 minutes and 3.56 W-hr/lb respectively. The actual 1.85V OCV indicates the probable presence of trace quantities of iron(III) in the cathode material. Removal of the iron(III) impurity would improve the performance of the FeCl_2 cathode in the same manner as would removal of CuCl_2 from CuCl .

Current Collector: The use of molybdenum (Alfa-Ventron, 99.7% pure) or nickel (Alfa-Ventron, 99.5% pure) powders in the place of graphite (Fisher, untreated) as an internal current collector in the cathode did not improve single cell performance, but drastically reduced the 80% ICCV output as shown in Table VIII. Graphite has proven

to be a superior internal current collector and because of cost and purity requirements of the other metallic current collectors tested will continue to be used.

Small quantities (no more than 1% of total pellet weight) of acetylene black in the $\text{LiAl}/\text{NaAlCl}_4/\text{MoCl}_5$ pelletized single cell produced a 2.5% increase in output as compared to a similar cell not containing this material. However, use of acetylene black in the WCl_6 single cell showed no increase in output. This suggests that the optimization of individual cathodes in our electrolyte for use in pelletized single cells is apparently unique. A single cell formula eventually may be deduced after further studies are undertaken.

The absence of graphite when using the semi-electronic conductors ZrS_2 and TiS_2 as cathodes showed no increased performance, as evidenced in the short lifetimes and low energy density at 80% ICCV of these single cells (Table IV). It was anticipated that these cells containing known semi-electronic conductors as cathodes (7), would give better energy density output due to their lower pellet weight with the absence of graphite. The use of graphite with these two compounds also gave poor 80% ICCV results.

Tests were also made to evaluate the effectiveness of various methods to purify graphite. Unpurified graphite and graphites purified by several methods were incorporated into single cells containing MoCl_5 . Table IX contains the results of these experiments. Fisher graphite purified by treatment in boiling HCl gave the best output at 175°C and 15 mA/cm^2 . Untreated Fisher graphite, known to contain impurities, gave the second best output. The poorest performance was graphite obtained from the Superior Graphite Company and subsequently purified.

The use of the purified Fisher graphite did not show a performance increase over the untreated Fisher graphite greater than the relative error established in a previous study (4). However, use of the purified Superior graphite did result in at least a 20% drop in performance.

FUTURE WORK

The three best cathodes selected in this study, WCl_6 , FeCl_3 , and TeCl_4 will be investigated in greater detail. Tests will be conducted at different current densities and temperatures to determine whether these potential cathodes might be advantageous for certain thermal battery applications. After optimization of these cathodes, a statistical analysis will determine if a general single cell formula for AlCl_3 based pelletized single cells can be formulated.

The role of acetylene black and the effectiveness of various methods to purify graphite will also be studied in greater detail.

REFERENCES

1. C.L. Hussey, J.K. Erbacher, and L.A. King, "High Energy Density Pelletized Aluminum Chloride Thermal Batteries," Report FJSRL-TR-76-0003, January 1976.
2. C.W. Jennings, "Thermal Batteries," The Primary Battery, Vol. Two, N.C. Cahoon and C.W. Heise, Ed., John Wiley and Sons, Inc., New York, NY, 1976, pp 263-293.
3. J.K. Erbacher, C.L. Hussey, and L.A. King, "The Discharge Behavior of an $\text{LiAl}/\text{NaAlCl}_4/\text{CuCl}_2$ Pelletized Thermal Cell," Report FJSRL-TR-77-0001, February 1977.
4. J.C. Nardi, J.K. Erbacher, C.L. Hussey, and L.A. King, "Experimental Optimization and Characterization of a $\text{LiAl}/\text{NaAlCl}_4/\text{MoCl}_5$ Pelletized Thermal Cell," Report FJSRL-TR-77-0002, February 1977.
5. M. Dowell, Union Carbide Corporation, Cleveland, OH, private communication, April 1977.
6. L.G. Boxall and R.A. Osteryoung, J. Electrochem. Soc., 121, 212 (1974).
7. D.A. Nissen, Sandia Laboratories, Albuquerque, NM, private communication, October 1976.

